

Comment on “Origin of Giant Optical Nonlinearity in Charge-Transfer–Mott Insulators: A New Paradigm for Nonlinear Optics”

Zhang [1] has proposed a novel mechanism for the giant optical nonlinearities in linear chain Nickel Halides (Ni-X) [2] and the cuprate Sr_2CuO_3 [3]. We show that Zhang’s theory is inapplicable to these systems and also, some of his numerical results are finite size artifacts. Although Zhang’s Hamiltonian for Ni-X is correct, the nature of the eigenstates depend crucially on the *relative* site energies of Ni and X in $\Delta \sum_{i,\sigma} (-1)^i n_{i,\sigma}$. Zhang chose the Ni atoms to occupy the odd sites in his exact diagonalization of $N = 8$ sites, such that the site energy of Ni is *lower* than that of X. There is then a competition between the on-site correlation U_{Ni} (which prefers Ni^{3+}) and Δ (which prefers Ni^{2+}), and near the interface, the nonlinear coefficient γ is huge for $\Delta < \Delta_c(U)$ and zero for $\Delta > \Delta_c(U)$ (see Fig. 1 of [1]). Based on earlier estimates of U and the *magnitude* of Δ , Zhang claims that Ni-X lie very close to the interface.

Zhang’s choice of the relative site energies is *opposite* to that of *all* previous authors [4,5], and can be precluded. Within the Ni^{3+} phase, the charge-transfer (CT) gap with conventional parametrization [4,5] increases with $(U_{\text{Ni}} - U_{\text{X}}) + V + 2\Delta$, whereas with Zhang’s choice the gap increases with $(U_{\text{Ni}} - U_{\text{X}}) + V - 2\Delta$. With a less diffuse valence atomic orbital in Cl, $U_{\text{Cl}} \geq U_{\text{Br}}$. Since, however, Cl is more electronegative than Br, 2Δ is larger for X = Cl with conventional parametrization [4,5] and compensates for the smaller $(U_{\text{Ni}} - U_{\text{X}})$ to give a larger optical gap in Ni-Cl, as is experimentally observed [5]. With Zhang’s choice of site energies, the only way to explain the larger CT gap in Ni-Cl is to make the unphysical assumption that 2Δ is smaller for Cl than Br, i.e., Cl is less electronegative than Br! Thus the conventional parametrization is correct. Hence there is no competition between U_{Ni} and Δ , and no enhancement of γ .

A second error in [1] involves the the sudden drop in γ by orders of magnitude to zero (see Fig. 1 of [1]). We show that this is a consequence of a crossover of the ground state from total spin $S = 0$ to $S = 1$, a finite size effect. It is well known that the ground state of a *finite* undistorted non-half-filled periodic ring with $4n$ electrons is $S = 1$. With $U_{\text{Ni}} \neq U_{\text{X}}$ and $V > 0$ this occurs at nonzero Δ . Zhang must have used a numerical approach that conserves total S_z and not total S . In Fig. 1(a) we have plotted $\Delta E = E(S_z = 1) - E(S_z = 0)$ for the parameters of Zhang’s Fig. 1. In all cases ΔE vanishes at *exactly* the same Δ_c as in [1]. Using a method that conserves total S , we have confirmed that for $\Delta < \Delta_c$, $E(S = 0) = E(S_z = 0)$, while for $\Delta > \Delta_c$, $E(S = 0) > E(S_z = 0)$. With specifically $N = 8$ and 12 electrons, the $S = 1$ ground state is not coupled to excited states by the current operator, and this is the

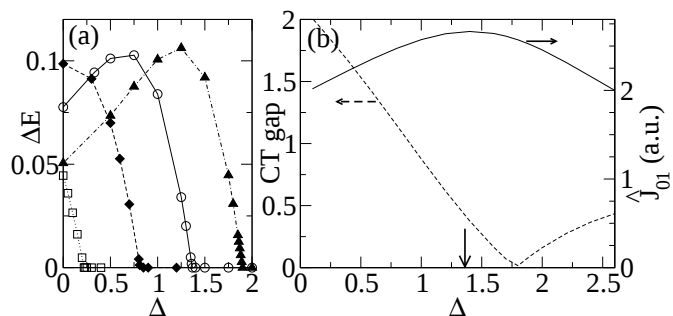


FIG. 1. (a) Energy difference between the lowest $S_z = 1$ and $S_z = 0$ states of the $N = 8$ periodic ring with 12 electrons, for, from left to right, $U_{\text{Ni}} = 2, 3, 4$ and 5 , with other parameters the same as in Fig. 1 of [1]. (b) The CT gap and the matrix element of the current operator $\hat{J}$ for $S = 0$ and $U_{\text{Ni}} = 4$. The arrow indicates the Δ where spin crossover occurs.

reason for the sharp drop in γ in [1]. We have confirmed that the spin crossover does not occur for $N = 12$ with 18 electrons. Also, the true Δ_c that defines the Ni^{3+} – Ni^{2+} interface is larger for all U . In Fig. 1(b) we have plotted the CT gap as well as the matrix element of the current operator $\hat{J}_{01}$ between the lowest $S = 0$ state and the $S = 0$ one-photon state for the $N = 8$ periodic ring, using the site energies in [1]. $\hat{J}_{01}$ is symmetric about the true Δ_c indicating a nearly symmetric behavior of γ even with Zhang’s parametrization.

To conclude: (i) Zhang’s choice of site energies for Ni-X are incorrect, (ii) his determination of Δ_c is incorrect, and (iii) the calculated behavior of γ for $\Delta > \Delta_c$ in [1] is an artifact of finite size calculations. Finally, the giant increase in γ near $\Delta_c(U)$ [1] within the model is largely due to decreasing CT gap rather than increasing $\hat{J}_{01}$. This does not permit device application, as losses due to absorption at wavelengths of interest would be large. We acknowledge useful discussions with A. Painelli and partial support from NSF-DMR.

R.T. Clay^{1,2} and S. Mazumdar¹

¹ Department of Physics, University of Arizona, Tucson, AZ 85721

² Cooperative Excitation Project ERATO, Japan Science and Technology Corporation (JST), University of Arizona, Tucson, AZ 85721

- [1] G.P. Zhang, Phys. Rev. Lett. **86**, 2086 (2001).
- [2] H. Kishida *et. al.*, Nature (London) **405**, 929 (2000).
- [3] T. Ogasawara *et. al.*, Phys. Rev. Lett. **85**, 2204 (2000).
- [4] H. Roder *et. al.*, Phys. Rev. Lett. **70**, 3498 (1993). M. Alouani *et. al.*, *ibid*, **71**, 1415 (1993). Y. Anusooya *et. al.*, J. Phys.-Condens Mat **11**, 2395 (1999).
- [5] H. Okamoto *et. al.*, Phys. Rev. B **54**, 8438 (1996).